



# Electromagnetic interference shielding effectiveness of polyaniline-nickel oxide coated cenosphere composite film



Pritom J. Bora<sup>a</sup>, K.J. Vinoy<sup>b</sup>, Praveen C. Ramamurthy<sup>a,c,\*</sup>, Kishore<sup>c</sup>, Giridhar Madras<sup>a</sup>

<sup>a</sup> Interdisciplinary Centre for Energy Research (ICER), Indian Institute of Science, Bangalore, India

<sup>b</sup> Department of Electrical and Communication Engineering, Indian Institute of Science, Bangalore, India

<sup>c</sup> Department of Materials Engineering, Indian Institute of Science, Bangalore, India

## ARTICLE INFO

### Keywords:

polymer-matrix composites (PMCs)  
thin films  
microstructures

## ABSTRACT

The solid waste material cenosphere (fly ash, by-product of thermal power plants) was nickel oxide nanoparticle coated (NiOC, core shell structure) by chemical heterogeneous precipitation and thermal reduction method. *in situ* synthesis of polyaniline (PANI) and NiOC composite (PNiOC) was carried out at  $-30 \pm 2^\circ\text{C}$  under nitrogen and characterized. The free standing films of as synthesized PNiOC composite were prepared by solution casting (followed by acid vapor treatment) and electromagnetic interference (EMI) shielding effectiveness (SE) was investigated in the J-band (5.8–8.2 GHz), X-band (8.2–12.4 GHz) and Ku-band (12.4–18 GHz). An average EMI SE of  $\sim 24$  dB,  $\sim 27$ –24 dB,  $\sim 21$  dB was observed for  $81 \pm 3$   $\mu\text{m}$  thicker flexible free standing PNiOC film in the J, X and Ku-band respectively. Effective EMI shielding due to absorption ( $SE_A$ ) was found to be dominant for PNiOC film. Unlike PANI emeraldine salt (ES) film, the EMI shielding due to absorption ( $SE_A$ ) was found more than two times higher for PNiOC film. Due to the presence of NiOC hollow microspheres in PANI, the time average power of incident electromagnetic wave decreases resulting in an increase of EMI SE ( $SE_A$ ). This film can be considered as a novel coating material for various applications such as unmanned vehicles, robotic and microwave engineering to protect against EMI.

## 1. Introduction

Intrinsic conducting polymers (ICP) have received tremendous attention because of its useful applications in sensors, batteries, actuators, microwave absorption and electromagnetic interference shielding (EMI shielding) [1–4]. Recently, electromagnetic interference (EMI) shielding materials are in demand due to the rapid use of radio or microwave frequencies for satellite-telecommunications, military applications etc. [4,5]. Moreover, these are non-ionizing electromagnetic radiations and have a bad impact on biological systems, animals and the environment [6]. By using conducting filler in polymer foams and films, EMI shielding and reflectance can be increased. The use of ICPs and its composites for EMI shielding has many advantages over traditional metallic sheets [5]. ICPs are lightweight, flexible and easy to synthesize [1,3,5,7]. The advantages of polyaniline over the ICPs are tuneable conductivity, adjustable permittivity/permeability, easy synthesis, low density, non-corrosiveness, good thermal and environmental stability [5,8–10]. In case of normally synthesized PANI, the presence of cross-linking is high, the conductivity is less and solution processing is difficult. The solution processing of PANI can be

performed in emeraldine base form (EB, semiconductor, which becomes conductor under protonic acid doping and converts to emeraldine salt) by using *N*-methyl-2-pyrrolidone (NMP) and dimethyl-propylene urea (DMPU). However, DMPU is believed as a better solvent [11,12].

Cenospheres, the by-products of power generating thermal plants, are considered as solid wastes and causes environmental pollution. Typically, these are hollow ceramic microspheres having alumina and silica as major constituents and are light-weight, low density and nontoxic. Moreover, it is highly dispersive in the polymer matrix [13–17]. Metal – cenosphere core shell has been proposed for many potential applications [13–20]. Many techniques have been employed for coating of cenosphere, e.g. magnetic sputtering, electroless plating, physical vapour deposition, sol-gel and heterogeneous precipitation thermal reduction method [17–20]. Heterogeneous precipitation results in homogenous unit distribution and requires inexpensive reactants. Surface treatment of cenosphere is important for microwave absorption; metal (Cu) deposited cenospheres have been reported for large band width ( $\sim 2$  GHz) microwave absorption at a minimum thickness ( $\sim 0.7$  mm) [21]. As conducting polymer, porous or hollow microsphere based composites are well known for microwave absorption, therefore

\* Corresponding author at: Interdisciplinary Centre for Energy Research (ICER), Indian Institute of Science, Bangalore, India.  
E-mail address: [onegroupb203@gmail.com](mailto:onegroupb203@gmail.com) (P.C. Ramamurthy).

PANI-cenosphere based systems has drawn attraction for microwave absorption as well as EMI shielding [22]. Magnetic nanoparticles coated cenospheres (core shell structure) i.e., soft magnetic microspheres have been reported as most suitable for microwave absorption [20,22]. However, most of the studies were carried out for powder pressed samples having thickness more than 2 mm. Recent advances in microwave engineering demands lightweight flexible thin films for microwave absorption and EMI shielding [4,5,11].

Nickel oxide (NiO) nanoparticles have been proposed for many potential applications including dielectrics [23,24]. The tremendous attention towards NiO nanoparticle is due to its superparamagnetic behaviour at room temperature and dielectric loss. Recently, it is reported that a.c. conductivity of polyaniline increases in the presence of NiO nanoparticle (especially at high frequency), which is also an important parameter for enhancing electromagnetic wave absorption [3,22]. The objective of the present work is the study of EMI shielding mechanism of multiphase nanocomposites (polyaniline -nickel oxide -cenosphere) in terms of the contribution of effective absorption and reflection to the total EMI shielding effectiveness.

## 2. Experimental

### 2.1. Chemicals

Cenospheres were obtained from National Thermal Power Corporation (NTPC), India, with particle size range of 15–70  $\mu\text{m}$ . These were separated by using 50  $\mu\text{m}$  sieve. Other chemicals used (AR grade) were procured from local suppliers.

### 2.2. Pretreatment of cenospheres

The cenospheres were cleaned before use. Typically, 5 g of FAC was dispersed in 5% NaOH solution followed by stirring with 1 M mixture of nitric acid ( $\text{HNO}_3$ ) and sulphuric acid ( $\text{H}_2\text{SO}_4$ ) at 3:1 ratio for 3 h at room temperature. Obtained precipitates were washed several times with deionised water and dried at 110  $^\circ\text{C}$  for 12 h.

### 2.3. Chemical synthesis of NiO coated cenosphere

Cleaned cenosphere was nickel oxide functionalized by heterogeneous precipitation thermal reduction method. Firstly, 2 g cenosphere were dispersed in 120 ml of PEG 800 (2 g) suspended aqueous solution. 0.5 M nickel nitrate solution ( $\text{Ni}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ ) and 1 M ammonium bicarbonate ( $\text{NH}_4\text{HCO}_3$ ) solution were gradually added at 3 ml/min (pH was maintained at 7–8). The solution was kept for stirring for 6 h at room temperature. The obtained precipitate was filtered and washed several times with deionised water and kept in oven at 80  $^\circ\text{C}$  for 12 h. Secondly, thermal reduction of this precursor was done at 600  $^\circ\text{C}$  for 3 h.

### 2.4. *in situ* synthesis of PANI-NiO-cenosphere composite

*in situ* synthesis of PANI-NiO-cenosphere (PNiOC) and PANI-cenosphere (PC) composites were carried out in nitrogen by oxidative polymerization of aniline in an immersion cooler (Julabo) [28]. Aniline was purified by immersing KOH pellets and then double distilled. 1 g of as prepared NiO-cenosphere was dispersed in 80 ml of 1 M HCl solution and 10 ml aniline was mixed at  $-30 \pm 2$   $^\circ\text{C}$ . To reduce the freezing temperature 6 M LiCl was added. Then the pre-cooled solution of ammonium persulphate (APS, 0.6 M) also in HCl (1 M, 80 ml), LiCl (6 M) was added at the rate of 3 ml/min using an external pump to the aniline solution. The reaction was allowed to proceed for 6 h at  $-30 \pm 2$   $^\circ\text{C}$ . The resulting precipitate was washed repeatedly with deionised water and deprotonated by stirring in 4 wt. % ammonia solution for 8 h at room temperature. The obtained composite precipitate was again washed with deionised water and methanol repeat-

edly. Finally it was kept in vacuum oven at 50  $^\circ\text{C}$  for 12 h. Similarly PANI-cenosphere and PANI were also synthesized under the same conditions.

### 2.5. Preparation of PANI-NiO-cenosphere composite film

Under stirring, 4 wt. % of synthesized PNiOC composite powder was added very slowly to the DMPU solvent. This mixture was further stirred for 5 h. The resulting solution was poured on to glass moulds and placed into an oven under a dynamic vacuum of 400 mm Hg at 70  $^\circ\text{C}$  for 12 h. Thus resulting films were acid vapor treated (1 M HCl) under vacuum for 72 h to achieve stable conductivity. Finally, it was dried under ultra-pure nitrogen. Similarly PANI-cenosphere (PC) and polyaniline film (PANI ES) was also prepared. The average thicknesses of PANI ES, PC and PNiOC films were found  $84 \pm 2$   $\mu\text{m}$ ,  $80 \pm 3$   $\mu\text{m}$  and  $81 \pm 3$   $\mu\text{m}$  respectively.

### 2.6. Characterizations

The synthesized samples were coated over carbon tape, sputter coated with gold and surface morphologies were examined by using high resolution FESEM (Carl Zeiss). The PANalytical X-ray diffractometer was used for collecting crystallographic data and crystallite size determination by using  $\text{Cu K}_\alpha$  radiation ( $\lambda = 1.540598$   $\text{\AA}$ ) in scattering range ( $2\theta$ ) of 10–80 $^\circ$  with a scan rate of 0.06 $^\circ$ /sec and slit width of 0.1 mm. The magnetic properties were investigated at room temperature by using a vibrating sample magnetometer (Lake Shore, Inc.). EMI SE measurement was carried out by using Agilent NS230A vector network analyzer. Thru-Reflect-Line (TRL) calibration was performed in the J-band (5.8–8.2 GHz), X-band (8.2–12.4 GHz) and Ku-band (12.4–18 GHz) before taking the measurements [25]. Three trials of each sample film was carried out by clamped tightly between two coaxial waveguide adapters and the S-parameters,  $S_{11}$  and  $S_{21}$ , were measured.

## 3. Results and discussion

### 3.1. Characterization of PANI-NiO-cenosphere composite

The surface morphology of cleaned cenosphere and NiO-cenosphere composite is shown in Fig. 1. The cenospheres are spherical hollow microspheres [17,22]. As shown in Fig. 1(c) and (d), surface morphology of NiO-cenosphere shows that NiO nanoparticles were coated over cenosphere surfaces almost homogeneously. However, some small agglomerated regions were also observed and is believed to be due to the magnetic dipole-dipole interaction between NiO nanoparticles as cenosphere is non-magnetic [20,22]. In case of defect bearing cenospheres the agglomerated regions are more prominent [22].

The obtained X-ray diffraction (XRD) patterns of NiO-cenosphere, PANI, PANI-NiO-cenosphere composites are shown in Fig. 2(a). The characteristic diffraction peaks of NiO-cenosphere at  $2\theta$  values of 37.53 $^\circ$ , 43.71 $^\circ$ , 63.51 $^\circ$  and 76.10 $^\circ$  correspond to (111), (200), (220) and (311) planes of NiO respectively. It was observed that the (200) plane of nickel oxide is the most intense. It is due to the minimum specific free energy of NiO at (200). The crystallite size was estimated from full width half maxima (FWHM) of the (200) plane by using Scherrer formula [26] and it was found  $\sim 32$  nm. The XRD pattern of PANI shows the amorphous nature and wide diffraction peaks were observed at  $\sim 15^\circ$  and  $\sim 25^\circ$  corresponds to periodicity (parallel and perpendicular) and the lower coherence length of PANI [27,28]. The obtained XRD patterns of composite sample (PNiOC) suggest the semi crystalline nature, both the NiO-cenosphere and PANI diffraction peaks were observed.

The magnetic properties of NiO-cenosphere and PANI-NiO-cenosphere composites were measured at 300 K and the obtained magnetization curves are shown in Fig. 2(b). The NiO-cenospheres and PANI-

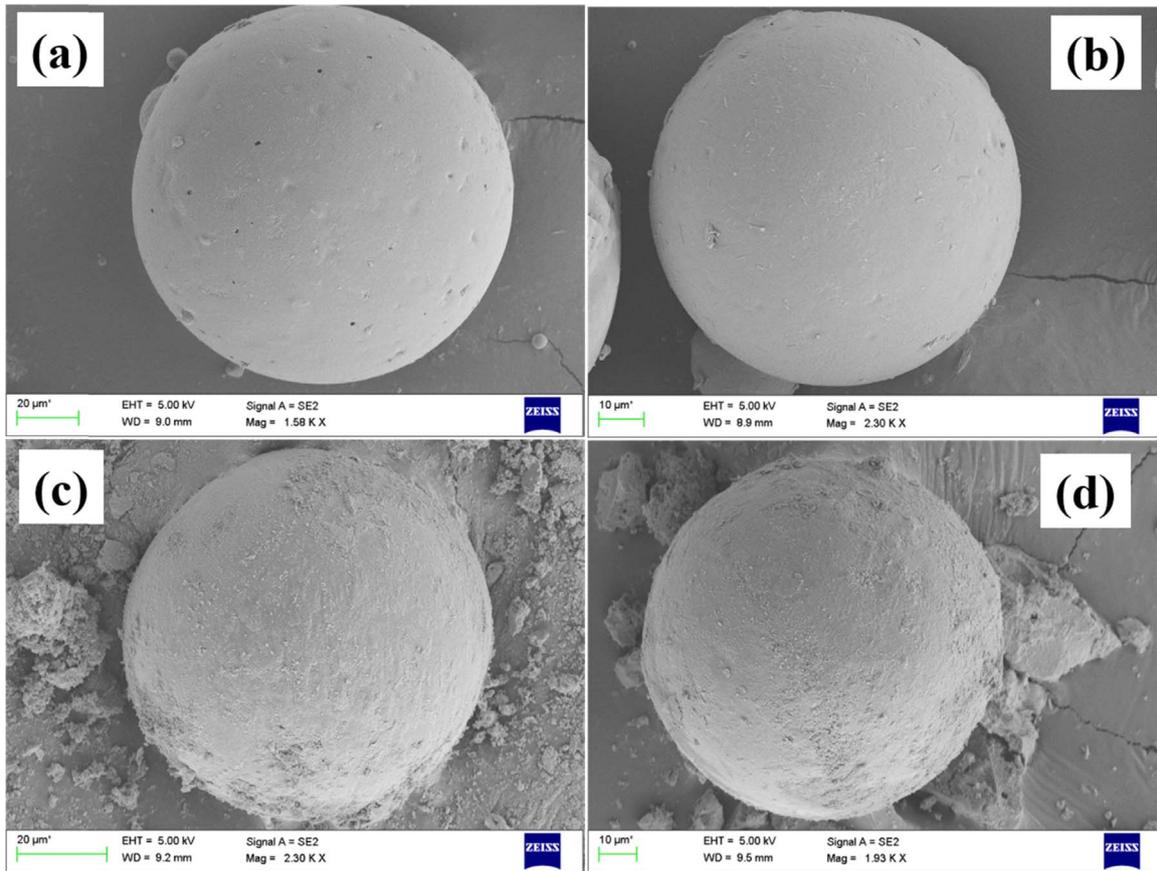


Fig. 1. Surface morphology of (a, b) cleaned cenospheres, (c, d) NiO coated cenospheres.

NiO-cenosphere composites exhibit soft magnetic behaviour. Saturation magnetization ( $M_s$ ) of PNiOC was found at 26.52 emu/kg. The EMI shielding due to absorption (microwave absorption) depends on the initial permeability ( $\mu_i$ ) value and it is related to saturation magnetization,  $M_s$  [9],

$$\mu_i = \frac{M_s^2}{aKH_c M_s + b\lambda\xi} \quad (1)$$

Where  $a$  and  $b$  are the two constants related to material composition,  $\lambda$ ,  $\xi$  and  $K$  are the magnetostriction constant, elastic strain parameter and proportionality constant respectively [9].

The surface morphologies of PNiOC films were shown in Fig. 3. Almost homogenous dispersion of NiO-cenosphere in PANI matrix was observed. Due to the presence of some defect bearing cenospheres and magnetic dipole interactions a few small agglomerated regions were noticed.

### 3.2. Electromagnetic interference (EMI) shielding of PNiOC film

Electromagnetic interference shielding refers to the protection of the propagation of electric and magnetic fields and it is the power of the incident electromagnetic wave ( $P_i$ ) to that of the transmitted wave ( $P_T$ ).

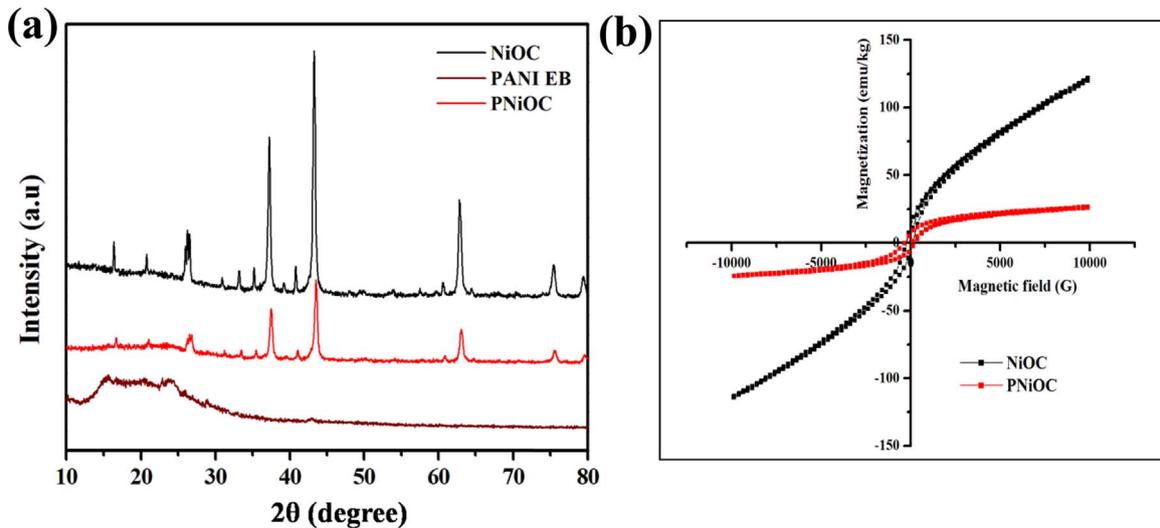


Fig. 2. (a) X-ray diffraction pattern and (b) hysteresis loop of NiO-cenosphere, PANI-NiO-cenosphere and PANI.

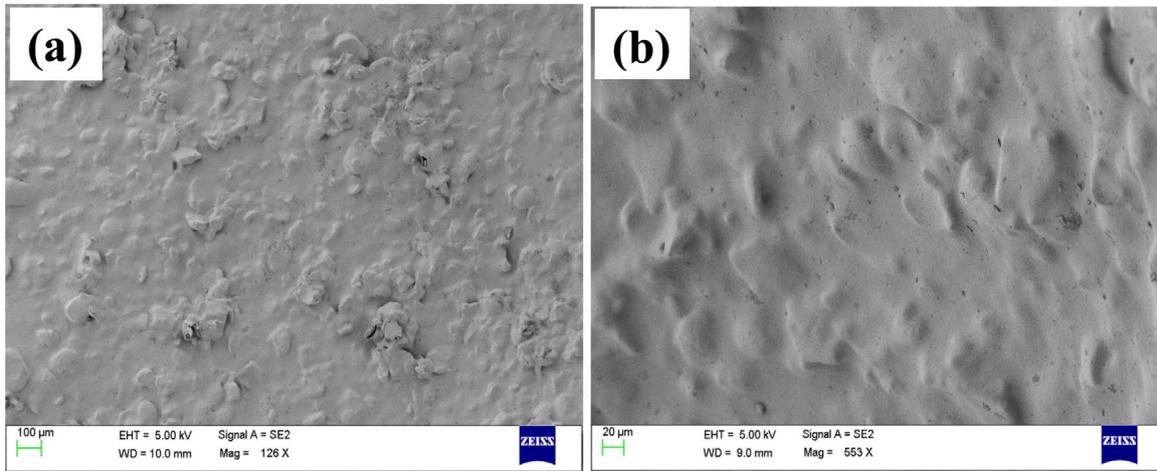


Fig. 3. Surface morphology of prepared PNiOC film at (a) low resolution and (b) at high resolution.

It takes place mainly due to reflection and absorption. Thus, EMI shielding effectiveness (SE) is resultant of the shielding due to reflection ( $SE_R$ ), absorption ( $SE_A$ ) and multiple reflections ( $SE_M$ ) in the following [4,33]:

$$SE(\text{dB}) = -10 \log \frac{P_t}{P_i} = SE_R + SE_A + SE_M \quad (2)$$

For electrically thick samples, the value of  $SE_M$  can be neglected if SE is  $\sim 10$  dB [5]. 20 dB EMI shielding effectiveness refers 99 % shielding [7]. Factors that effects on EMI attenuation are shield conductivity, permittivity and permeability, frequency, distance between the shielded and interfering source, shield thickness and shield materials [3,35]. The  $S$  parameters  $S_{11}$  (or  $S_{22}$ ) and  $S_{12}$  (or  $S_{21}$ ) of a two port network system represents the reflection and transmission coefficients respectively [25]. The value of EMI SE is equivalent to the attenuation on transmission ( $|S_{12}|$  or  $|S_{21}|$ ) of the radiation [29]. The absorbance ( $A$ ), reflectance ( $R$ ) and transmittance ( $T$ ) of the prepared films were obtained from the measured  $S$ -parameters [22]. The value of  $A$  depends on the power of the incident electromagnetic wave, the relative intensity of the effectively incident electromagnetic wave inside the materials after reflection is based on the quantity  $(1-R)$ . Therefore, the effective absorbance ( $A_{\text{eff}}$ ) is given by [30],

$$A_{\text{eff}} = (1-R - T)/(1-R). \text{ Conventionally}$$

$$SE_R(\text{dB}) = -10 \log (1-R) \quad (3)$$

$$SE_A(\text{dB}) = -10 \log (1 - A_{\text{eff}}) = -10 \log \frac{T}{1-R} \quad (4)$$

Obtained EMI SE of PANI ES, PC and PNiOC composite films in the J-band (5.8–8.2 GHz), X-band (8.2–12.4 GHz) and Ku-band (12.4–18 GHz) frequency range shown in Figs. 4–6 (along with  $SE_A$  and  $SE_R$ ). In the J-band (Fig. 4(a) and (b)), the average EMI SE of PC and PNiOC film is  $\sim 18$  dB and  $\sim 24$  dB respectively, which is much higher than PANI ES film ( $\sim 15$  dB). The obtained  $SE_A$  value of PANI ES was  $\sim 9$  dB ( $SE_R$  was  $\sim 6$  dB) which increases to  $\sim 13$  dB ( $SE_R$  was  $\sim 5$  dB) and  $\sim 20$  dB ( $SE_R$  was  $\sim 4$  dB) for PC and PNiOC film respectively. Similarly, in the X-band (Fig. 5(a) and (b)), the EMI SE of PANI ES, PC and PNiOC film were found to be 19–17 dB ( $SE_A \sim 10$ –12 dB,  $SE_R \sim 9$ –7 dB), 22–19 dB ( $SE_A \sim 15$ –13 dB,  $SE_R \sim 7$ –6 dB) and 27–24 dB ( $SE_A \sim 20$ –21 dB,  $SE_R \sim 7$ –3 dB) respectively. As shown in the Fig. 6(a) and (b), the EMI SE of PANI ES, PC and PNiOC film was found to be 14–12 dB ( $SE_A \sim 9$ –7,  $SE_R \sim 5$  dB), 16–14 dB ( $SE_A \sim 12$ –10 dB,  $SE_R \sim 4$  dB) and 21–19 dB ( $SE_A \sim 18$ –16 dB,  $SE_R \sim 3$  dB) respectively in the Ku-band. Thus, EMI shielding due to absorption was found to be intrinsically dominant for all the films in the J, X and Ku-band. The observed variation of EMI SE with frequency is believed to be the unique shielding property of the PNiOC film. As PNiOC film has

multi-phases, therefore due to polarization effect and electrical loss EMI shielding varies with frequency nonlinearly [36]. Moreover, multiple reflection is another important factor for observed nonlinear EMI shielding property of the prepared composite films [37]. The important design parameter for EMI shielding is the thickness of the shield. According to Simon formalism, EMI SE can be expressed as [38],

$$EMI SE = 50 + 10 \log(\sigma_{mw}/f) + 1.7t \sqrt{\sigma_{mw}f} \quad (5)$$

Here  $t$  represents thickness of the shield (cm),  $\sigma_{mw}$  is the shield conductivity and  $f$  is the frequency (MHz). Thus, EMI SE of PC, PNiOC films can be increased by increasing film thickness. However, here it was observed that the PNiOC film exhibits 99% EMI shielding efficiency at the thickness of  $81 \pm 3 \mu\text{m}$  and it is potentially useful to coat over any substrate.

The time average power of incident electromagnetic wave decreases inside a material. Mathematically,  $P_{av} = \frac{1}{2} \int (E \times H^*) dS$ , where  $E$  refers electric field and  $H$  refers magnetic field and the asterisk indicates corresponding complex conjugate of it and it travels by changing phase and exponentially decreasing the magnitude [31]. Here, PANI surface supports the incident normal electric field and embedded NiO-cenosphere is supporting tangential magnetic and electric field components of incident electromagnetic wave. The time varying magnetic fields interacts with magneto-dielectric layer and thus electric loss takes place over the cenosphere surface [31,32]. Moreover, some of the radiation was absorbed within the cenosphere as magneto-dielectric system is useful for impedance matching as well as microwave absorption [14,32,33]. The factor which strongly effect on EMI shielding due to absorption is skin depth ( $\delta$ ). It is defined as the distance up to which the intensity of the electromagnetic wave decreases to  $1/e$  of its original strength [4,30],  $\delta = \sqrt{2/\mu_0 \mu' \omega \sigma_{mw}}$ , where,  $\mu'$  is the real part of complex permeability ( $\mu^* = \mu' - i\mu''$ ),  $\omega$  is the angular frequency,  $\sigma_{mw}$  is the shield conductivity and it can be expressed as,  $\epsilon_r = \epsilon' - i \frac{\sigma_{mw}}{\epsilon_0 \omega}$ . Thus, it indicates that the conductive loss and dielectric relaxation loss (corresponds to  $\epsilon''$ ) decreases with frequency [39]. According to transmission line theory, the effective absorption is dominated by impedance matching and EM attenuation in the interior absorber. In the PC and PNiOC film, the dielectric and magneto dielectric hollow microspheres (NiO-cenosphere) are dispersed optimally, therefore electromagnetic wave has to pass through it and high EM attenuation takes place. The presence of hollow microspheres in polymer matrix is useful for microwave absorption. However, use of high dielectric hollow microspheres has benefits. The mathematical module for this kind of layered structure has recently proposed by Bychanok et.al [40]. As cenosphere were coated by NiO and followed by conducting polymer, it is superior for microwave absorption. For far field, the long wave approximation can be applicable. Hence, the type of ordering of hollow microspheres

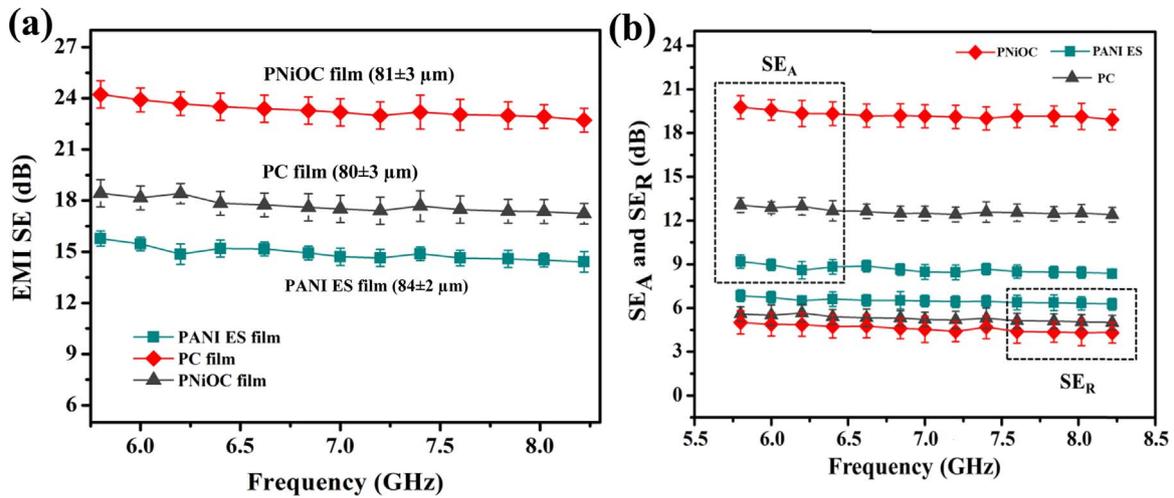


Fig. 4. (a) EMI shielding effectiveness in dB, (b) EMI shielding due to absorption SE<sub>A</sub> (dB), and the shielding due to reflection SE<sub>R</sub> (dB) of PANI ES, PANI-cenosphere (PC) and PANI-NiO cenosphere (PNiOC) nanocomposite films in the J-band (5.8–8.2 GHz).

in the mono layer does not significantly affect the EM absorption properties [40]. In the PNIOc film, the presence of NiO-cenosphere introducing a homogenisation for the spatial dispersion of the effective media [40]. As magnetic loss was observed to be less for PNIOc composite, therefore R, T can be expressed as [41],

$$R = \frac{(Z_R - 1)}{(Z_R + 1)} \quad (6)$$

Here,

$$Z_R = [1 + j(Z/Z_0) \tan(kt)] / [1 + j(Z_0/Z) \tan(kt)] \quad (7)$$

$j$  represents the unit imaginary number and  $Z_0 = (\mu_0/\epsilon_0)^{1/2} = 377 \Omega$ .

$$Z = \left[ \mu_0 \left( \epsilon + \frac{\sigma_{mw}}{j\omega} \right) \right]^{1/2} \quad (8)$$

$$k = \omega \left[ \mu_0 \left( \epsilon + \frac{\sigma_{mw}}{j\omega} \right) \right] \text{ and}$$

$$T = (1+R)\cos(kt) - j(Z/Z_0)(1-R)\sin(kt) \quad (9)$$

This is also important to note here that the thin films may absorb up to half of the incident power even if the thin film thickness  $t$  is much less than the skin depth [41]. Apart from this, enhancement of anisotropic energy, interfacial polarizations and the synergetic effect in between PANI and NiO-cenosphere can be considered as another

reason for the enhanced EMI SE as well as shielding due to absorption [32–34].

#### 4. Conclusions

In Summary,

1. The free standing film of *in situ* synthesized ( $-30 \pm 2^\circ \text{C}$ ) PANI-NiO coated cenosphere composite was prepared by solution processing.
2. The EMI SE of these films were investigated in the J, X and Ku-band and the shielding mechanism of this multiphase composite was studied.
3. The  $81 \pm 3 \mu\text{m}$  thicker PNIOc film shows the most appreciable EMI SE  $\sim 20$  dB (corresponds to 99% shielding).
4. EMI shielding due to absorption was found to be intrinsically predominant for PNIOc film (comparatively, PANI (ES) film it is two times higher).
5. As prepared PNIOc film is a novel inexpensive coating material to protect against EMI especially for communication devices, robotics and microwave engineering.

#### Acknowledgments

Authors gratefully acknowledge the financial support by Department of Science and Technology, SB/S3/ME/51/2012 and

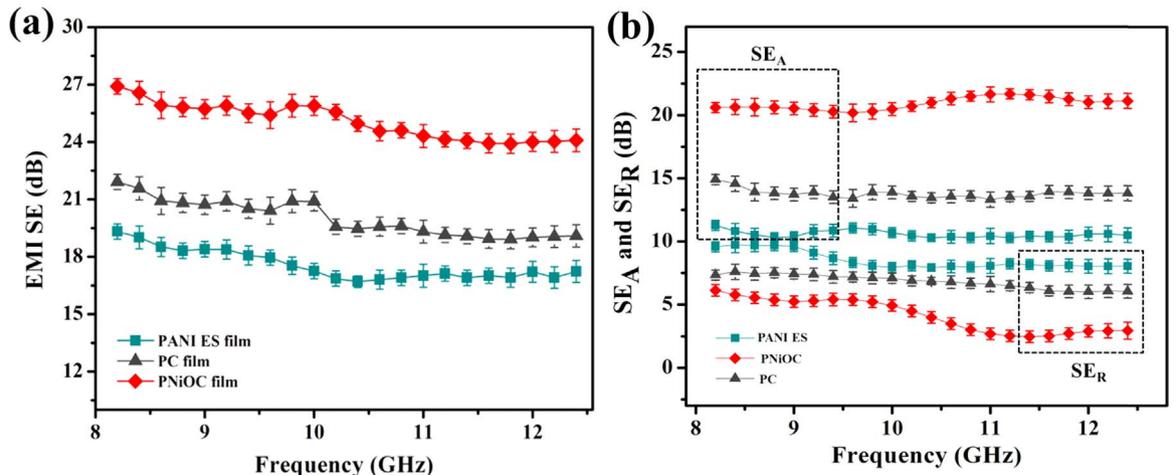


Fig. 5. (a) EMI shielding effectiveness in dB, (b) EMI shielding due to absorption SE<sub>A</sub> (dB), and the shielding due to reflection SE<sub>R</sub> (dB) of PANI ES, PANI-cenosphere (PC) and PANI-NiO cenosphere (PNiOC) nanocomposite films in the X-band (8.2–12.4 GHz).

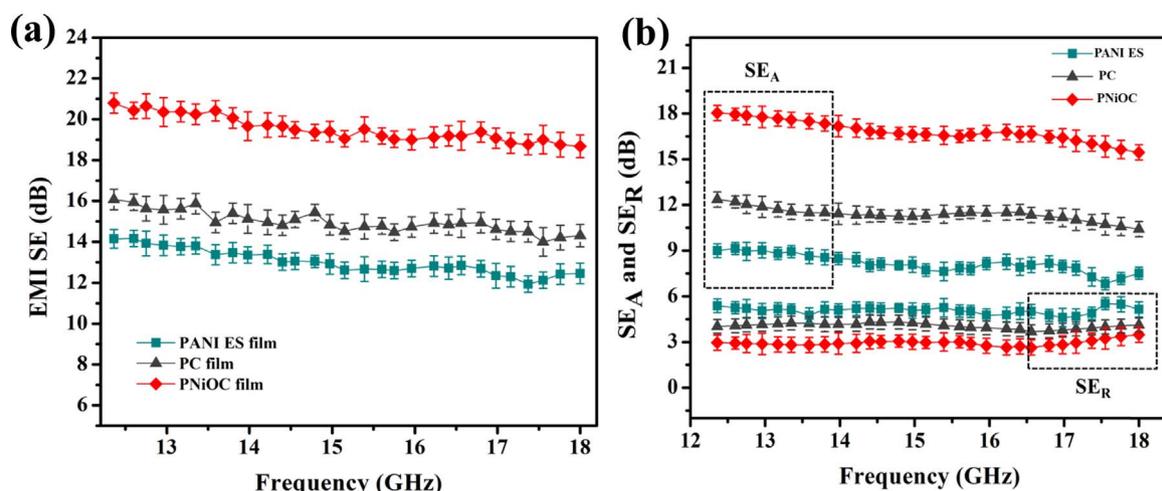


Fig. 6. (a) EMI shielding effectiveness in dB, (b) shielding due to absorption  $SE_A$  (dB), and the shielding due to reflection  $SE_R$  (dB) of PANI ES, PANI-cenosphere (PC) and PANI-NiO cenosphere (PNiOC) nanocomposite films in the Ku-band (12.4–18 GHz).

technical support from IISc advanced characterization centre and CeNSE for this work. Kishore would like to place on record the AICTE for offering Emeritus position and Prof. G. S. Gupta of Department of Materials Engineering, IISc for providing administrative support.

## References

- G. Ćirić-Marjanović, Recent advances in polyaniline composites with metals, metalloids and nonmetals, *Synth. Met.* 170 (2013) 31–56.
- J. Luo, Y. Chen, Q. Ma, R. Liu, X. Liu, Layer-by-layer assembled ionic-liquid functionalized graphene-polyaniline nanocomposite with enhanced electrochemical sensing properties, *J. Mater. Chem. C* 2 (2014) 4818–4827.
- P. Saini, V. Choudhary, B.P. Singh, R.B. Mathur, S.K. Dhawan, Polyaniline-MWCNT nanocomposites for microwave absorption and EMI shielding, *Mater. Chem. Phys.* 113 (2009) 919–926.
- P.J. Bora, M. Porwal, K.J. Vinoy, P.C. Ramamurthy, G. Madras, Influence of MnO<sub>2</sub> decorated Fe nano cauliflowerers on microwave absorption and impedance matching of polyvinylbutyral (PVB) matrix, *Mater. Res. Express* 3 (2016) 95003.
- P.J. Bora, G. Lakhani, P.C. Ramamurthy, G. Madras, Outstanding electromagnetic interference shielding effectiveness of polyvinylbutyral-polyaniline nanocomposite film, *RSC Adv.* 6 (2016) 79058–79065.
- B. Hileman, Radiofrequency and microwave radiation, *Environ. Sci. Technol.* 16 (1982) 442A–444A.
- M.H. Al-Saleh, W.H. Saadeh, U. Sundararaj, EMI shielding effectiveness of carbon based nanostructured polymeric materials: a comparative study, *Carbon* 60 (2013) 146–156.
- A.G. MacDiarmid, J.C. Chiang, A.F. Richter, A.J. Epstein, Polyaniline: a new concept in conducting polymers, *Synth. Met.* 18 (1987) 285–290.
- P. Saini, V. Choudhary, N. Vijayan, R.K. Kotnala, Improved electromagnetic interference shielding response of poly(aniline)-coated fabrics containing dielectric and magnetic nanoparticles, *J. Phys. Chem. C* 116 (2012) 13403–13412.
- S.-W. Phang, T. Hino, M.H. Abdullah, N. Kuramoto, Applications of polyaniline doubly doped with p-toluene sulphonic acid and dichloroacetic acid as microwave absorbing and shielding materials, *Mater. Chem. Phys.* 104 (2007) 327–335.
- P.C. Ramamurthy, A.N. Mallya, A. Joseph, W.R. Harrell, R.V. Gregory, Synthesis and characterization of high molecular weight polyaniline for organic electronic applications, *Polym. Eng. Sci.* 52 (2012) 1821–1830.
- K.T. Tzou, R.V. Gregory, Improved solution stability and spinnability of concentrated polyaniline solutions using N,N'-dimethyl propylene urea as the spin bath solvent, *Synth. Met.* 69 (1995) 109–112.
- A. Kumar, *Industrial Pollution: problems and Solutions*, Daya Publishing House, 2006.
- W. Fu, S. Liu, W. Fan, H. Yang, X. Pang, J. Xu, et al., Hollow glass microspheres coated with CoFe<sub>2</sub>O<sub>4</sub> and its microwave absorption property, *J. Magn. Magn. Mater.* 316 (2007) 54–58.
- W. Wang, Q. Li, Y. Li, H. Xu, J. Zhai, Electroless Ag coating of fly ash cenospheres using polyaniline activator, *J. Phys. Appl. Phys.* 42 (2009) 215306.
- B. Wang, Q. Li, J. Kang, J. Pang, W. Wang, J. Zhai, Preparation and characterization of polypyrrole coating on fly ash cenospheres: role of the organosilane treatment, *J. Phys. Appl. Phys.* 44 (2011) 415301.
- A.S. Roy, S. Saravanan, Kishore, P.C. Ramamurthy, G. Madras, Dielectric impedance studies of poly(vinyl butyral)-cenosphere composite films, *Polym. Compos.* 35 (2014) 1636–1643.
- X. Yu, Z. Xu, Z. Shen, Metal copper films deposited on cenosphere particles by magnetron sputtering method, *J. Phys. Appl. Phys.* 40 (2007) 2894.
- X. Yu, Z. Shen, The electromagnetic shielding of Ni films deposited on cenosphere particles by magnetron sputtering method, *J. Magn. Magn. Mater.* 321 (2009) 2890–2895.
- X. Meng, D. Li, X. Shen, W. Liu, Preparation and magnetic properties of nano-Ni coated cenosphere composites, *Appl. Surf. Sci.* 256 (2010) 3753–3756.
- M. Qianjin, Y. Caixia, G. Kaiyong, Z. Meiling, Microwave Absorption Characteristics of Surface Treated Fly-ash Cenosphere Particles, *Journal of Tsinghua University (Science and Technology)*, 2005 (12).
- P.J. Bora, N. Mallik, P.C. Ramamurthy, Kishore, G. Madras, Poly(vinyl butyral)-polyaniline-magnetically functionalized fly ash cenosphere composite film for electromagnetic interference shielding, *Compos Part B: Eng.* 106 (2016) 224–233.
- B.M. Patil, G. Sharanappa, AC conductivity of polyaniline – nickel oxide composite, *Int. J. Adv. Res. Eng. Appl. Sci.* 2 (2013) 80–85.
- V. Biju, M. Abdul Khadar, Analysis of AC electrical properties of nanocrystalline nickel oxide, *Mater. Sci. Eng.: A* 304–306 (2001) 814–817.
- L.F. Chen, C.K. Ong, C.P. Neo, V.V. Varadan, V.K. Varadan, *Microwave Electronics: measurement and Materials Characterization*, John Wiley & Sons, 2004.
- B.D. Cullity, S.R. Stock, *Elements of X-Ray Diffraction: Pearson New International Edition*, Pearson Education, Limited, 2013, <<https://books.google.co.in/books?id=F81wngEACAAJ>>.
- J.P. Pouget, M.E. Jozefowicz, A.J. Epstein, X. Tang, A.G. MacDiarmid, X-ray structure of polyaniline, *Macromolecules.* 24 (1991) 779–789.
- N. Gandhi, K. Singh, A. Ohlan, D.P. Singh, S.K. Dhawan, Thermal, dielectric and microwave absorption properties of polyaniline-CoFe<sub>2</sub>O<sub>4</sub> nanocomposites, *Compos. Sci. Technol.* 71 (2011) 1754–1760.
- Y. Yang, M.C. Gupta, K.L. Dudley, R.W. Lawrence, Novel carbon nanotube – polystyrene foam composites for electromagnetic interference shielding, *Nano Lett.* 5 (2005) 2131–2134.
- Y.K. Hong, C.Y. Lee, C.K. Jeong, D.E. Lee, K. Kim, J. Joo, Method and apparatus to measure electromagnetic interference shielding efficiency and its shielding characteristics in broadband frequency ranges, *Rev. Sci. Instrum.* 74 (2003) 1098–1102.
- C.A. Grimes, D.M. Grimes, A brief discussion of EMI shielding materials, in: *IEEE Aerospace Applications Conference, Dig.*, 1993, pp. 217–226.
- R. Moore, *Electromagnetic Composites: models, Measurement and Characterization*, You Lulu Inc., 2014, <<https://books.google.co.in/books?id=4QDxBQAAQBAJ>>.
- A. Ohlan, K. Singh, A. Chandra, S.K. Dhawan, Microwave absorption behavior of core-shell structured poly(3,4-ethylenedioxy thiophene)-barium ferrite nanocomposites, *ACS Appl. Mater. Interfaces* 2 (2010) 927–933.
- A.P. Singh, A.K. S. A. Chandra, S.K. Dhawan, Conduction mechanism in Polyaniline-flyash composite material for shielding against electromagnetic radiation in X-band & Ku band, *AIP Adv.* 1 (2011) 022147.
- S. Varshney, A. Ohlan, V.K. Jain, V.P. Dutta, S.K. Dhawan, In situ synthesis of polypyrrole-γ-Fe<sub>2</sub>O<sub>3</sub>-Fly Ash Nanocomposites for Protection against EMI Pollution, *Ind. Eng. Chem. Res.* 53 (2014) 14282–14290.
- G. Sudheer Kumar, D. Vishnupriya, A. Joshi, S. Datar, T. Umasankar Patro, Electromagnetic interference shielding in 1–18 GHz frequency and electrical property correlations in poly(vinylidene fluoride)-multi-walled carbon nanotube composites, *Phys. Chem. Chem. Phys.* 17 (2015) 20347–20360.
- J. Joo, A.J. Epstein, Electromagnetic radiation shielding by intrinsically conducting polymers, *Appl. Phys. Lett.* 65 (1994) 2278–2280.
- F. Shahzad, M. Alhabeib, C.B. Hatter, B. Anasori, S.M. Hong, C.M. Koo, Y. Gogotsi, Electromagnetic interference shielding with 2D transition metal carbides (MXenes), *Science.* 353 (2016) 1137–1140.
- T. Kasagi, T. Tsutaoka, K. Hatakeyama, Electromagnetic properties of Permenur granular composite materials containing flaky particles, *J. Appl. Phys.* 116 (2014) 153901.
- D. Bychanok, S. Li, A. Sanchez-Sanchez, G. Gorokhov, P. Kuzhir, F.Y. Ogrin, A. Pasc, T. Ballweg, K. Mandel, A. Szczurek, V. Fierro, A. Celzard, Hollow carbon spheres in microwaves: bio inspired absorbing coating, *Appl. Phys. Lett.* 108 (2016) 013701.
- H. Bosman, Y.Y. Lau, R.M. Gilgenbach, Microwave absorption on a thin film, *Appl. Phys. Lett.* 82 (2003) 1353–1355.